



Performance of electrical discharge textured cutting tools

P. Koshy (2), J. Tovey

Department of Mechanical Engineering, McMaster University, Hamilton, Canada

Abstract: Tool face friction adversely affects chip formation and consumes about 25% of the total cutting energy. Friction in cutting can be controlled by introducing a lubricant into the tool-chip interface, the effectiveness of which may be enhanced by surface texturing the tool. This paper details the innovative application of electrical discharge machining for generating an isotropic texture on the tool rake face, with a view to facilitating lubricant penetration and retention. A significant reduction in feed and cutting forces that ensues from said texturing is demonstrated, followed by a presentation of the features and application areas of the technology.

Keywords: Electrical discharge machining (EDM), Cutting tool, Surface texturing

1. Introduction

The influence of lubrication on chip formation was first reported by Mallock about 130 years ago in one of the first papers ever published on machining [1]. Theoretical analyses and intricate experiments have since enabled a fair insight into the nature of cutting friction. It is now understood that the high normal stresses in the vicinity of the cutting edge precludes lubricant penetration therein, and that lubricant infiltration into the tool-chip interface occurs through micro-channels in the rear of the contact away from the edge. The transport of liquid lubricants into the tool-chip interface is governed by the mechanisms of capillary action that promotes it and chip velocity-induced shear flow that restrains it. As the effectiveness of a lubricant is dependent on the time available for it to be adsorbed into and/or chemically react with the chip to reduce the interfacial shear strength, retention of the lubricant in the interface is as critical as its ingress.

One avenue to promoting lubrication is surface texturing, which refers to appropriately structuring the topography of a functional surface [2]. Commonly known surfaces that entail a texture to control friction are generated in such processes as honing, scraping and knurling, wherein the texture is essentially continuous. Surface textures can also be discrete to comprise an array of microscopic dimples or a series of grooves distributed over the surface, which serve to reduce friction and wear by functioning as micro-bearings and debris traps, respectively.

The literature on tribological applications of surface texturing predominantly refers to automotive components such as bearings, seals and piston ring assemblies. Notwithstanding the significant potential, attempts at extending this concept to cutting tools have been relatively few and recent. Enomoto et al [3] present experimental evidence to show that nanoscale grooves on the tool rake face are more effective than microscale grooves in decreasing friction and adhesion when face milling aluminum. Similar results have been reported by Kawasegi et al [4] in turning of aluminum. Lei et al [5] machined micro-hole arrays on the tool rake face with a view to facilitating lubrication, and

observed a 10–30% reduction in machining force when turning steel. Jiang et al [6] demonstrated the prospect of friction reduction in tooling applications by electrostatic spray coating a soft lubricant layer over a textured hard coating, with the latter biomimetically structured to resemble the topography of a lotus leaf for enhanced lubrication.

Texturing techniques span a wide spectrum of diverse technologies ranging from chemical etching to forming, a review of which can be found in [2]. In the cutting tool applications mentioned previously [3–5], femtosecond lasers have been used to fabricate microscale textures through conventional ablation, and nanoscale textures through laser-induced periodic structuring brought about by laser interference. As fine and versatile femtosecond laser texturing is, the technology is limited by throughput: texturing 64 mm² of TiN-coated steel with dimples of depth 18 μm at a pitch of 80 μm corresponds to a processing time of about 25 minutes [7]. Alternatively, through-mask electrochemical machining [8] may be employed; however, the corresponding dimple size is larger, reportedly on the order of 250 μm, which increases the likelihood of the chip material extruding into and clogging the texture [3–5], thus affecting its function and performance.

In the context of the background presented above, this paper proposes the innovative application of sink electrical discharge machining (EDM) for the rapid texturing of the rake face of a cutting tool with the intent of promoting lubrication in the tool-chip interface. This idea is conceptually different from texturing of steel rolls using EDM [9] wherein the objective is to transfer the spark eroded texture from the roll onto sheet steel or aluminum, during the rolling operation.

The motivations toward using EDM for texturing cutting tools are several. As material removal in EDM inherently entails high-frequency localized melting and vaporization at the microscale, the generated surface comprises a large number of microscopic, overlapping craters. Accordingly, EDM is one of the few processes with the capability to generate surfaces with a

positive skewness [10], which means that the surface consists of peaks interspersed among relatively wide valleys that are ideally predisposed to entraining lubricant. As highlighted in [3,4], textures are preferably oriented normal to the chip velocity vector with a view to limiting chip flow from expediting the egress of lubricant from the tool-chip contact zone; to this end, the isotropic nature of EDM surfaces is advantageous, as it renders the texture performance to be independent of the direction of chip flow. EDM further offers the flexibility to tailor the size and shape of the characteristic craters that collectively constitute the texture towards a specific application, by tuning the pulse parameters.

2. Experimental

The objective of the experimental work was to prove the concept of electrical discharge texturing of cutting tools, and to determine the envelope of EDM and cutting parameters in which such textures are effective in reducing friction. Texture performance was assessed in continuous and intermittent orthogonal cutting, realized in a turning process by appropriately configuring the workpiece geometry. Experiments involved annealed 1045 steel and 6061 aluminum workpieces, with the textures evaluated in terms of cutting (F_c) and feed (F_f) force components.

This research referred to two types of textures. The areal texture schematically represented in Fig. 1a was machined by using sink EDM with a block electrode, such that the texture was continuous, comprising overlapping craters typical of surfaces generated in EDM. Machining was accomplished in an oil-based dielectric, in a machine tool equipped with a solid state power supply, with copper electrodes in positive polarity. In generating the textures, an average gap voltage of 100 V and a duty factor of 0.5 were maintained, and the discharge current (i_e) and on-time (t_i) were varied up to a maximum of 72 A and 133 μ s, respectively. To compare the performance of the continuous texture, limited tests related to a discrete linear texture (Fig. 1b) comprising grooves of depth and width of about 100 μ m, which ran parallel to the cutting edge. These grooves were also machined by sink EDM using thin shim stock tooling. The location of the texture with respect to the cutting edge along the length of the tool, as specified by the distance d_e (see Fig. 1a), was found to markedly affect its performance, and hence the influence of this parameter was also investigated.

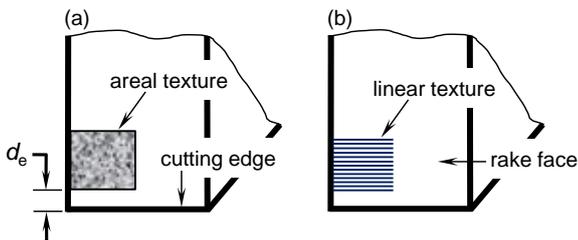


Fig. 1. Texture position and configurations.

The cutting tools used in the experiments were finish-ground T-15 grade high speed steel inserts of SPG 432 geometry, with a 0° rake angle. The flat rake face of this insert type facilitated easy texturing. Cutting experiments corresponded to the cutting speed (v_c) and the feed (h) varied in the range of 2–75 m/min and 0.025–0.1 mm, respectively, with the cut width held constant at 3 mm. As shown in Fig. 1, the textures were designed to extend just half way across the tool width of 12.5 mm, so that reference cutting force data corresponding to the non-textured ground surface could be obtained with minimal tool-related variability,

by just shifting the tool laterally by a distance more than the cutting width. The orientation of the insert was such that the surface lay on the ground surface was parallel to the cutting edge for better lubrication, relative to a lay that is perpendicular. A light-duty cutting oil (Chem Ecol 250A, 35 mm^2/s viscosity at 40 $^\circ\text{C}$) with synthetic fat additives was used as the lubricant, which was applied as a flood along the tool rake face.

3. Results and discussion

Fig. 2 compares the evolution of the friction angle for textured and non-textured tools, with the shaded vertical bars indicating intervals over which the lubricant was applied. The friction angle is a measure of lubrication effectiveness, and is given by $\tan^{-1}(F_f/F_c)$ for a rake angle of 0° . This test corresponded to continuous cutting of steel at $v_c = 2$ m/min and $h = 0.1$ mm, with a continuous texture (Fig. 1a) referring to optimized EDM parameters of $i_e = 39$ A and $t_i = 42$ μ s, and $d_e = 0.2$ mm. All results reported in this paper refer to conditions above, unless noted otherwise. The effects of these parameters themselves are discussed later.

While the friction angle referring to the non-textured tool remained essentially stationary (Fig. 2b), the textured tool exhibited a conspicuous decrease over the intervals referring to lubricant application (Fig. 2a). This conclusively shows the effectiveness of the texture in enhancing lubrication at the tool-chip interface. As the ingress of the lubricant into the contact zone is by capillary action [1] that occurs in a time on the order of milliseconds, the effect of lubricant application in reducing friction is rather instantaneous (Fig. 2a). Similarly, the friction angle reverts back as soon as the lubricant flow is interrupted, as the tool chip interface is immediately starved of the lubricant, which is consumed in reaction with the nascent chip surface and transported off the contact zone.

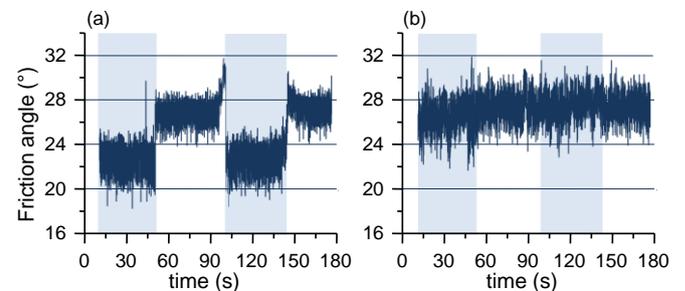


Fig. 2. Evolution of friction angle for: (a) textured; and (b) non-textured tools; shaded regions denote lubricant application.

During the texturing process, care was taken to limit the depth of the texture into the rake face, in order to prevent the tool from functioning as a restricted rake tool. This refers to a tool with a secondary rake face at an acute angle towards the tool flank, with a view to limiting the contact length [1]. Despite the consequent reduction in forces, such tools can in actual fact correspond to an increase in tool stresses and temperature that adversely affect tool performance, on account of insufficient material in the tool wedge. The friction angle assuming values similar to a non-textured tool on suspending lubricant flow (Fig. 2a) signifies that the texturing did not render the tool to be of restricted rake. This was further verified in experiments wherein the rake face of a textured tool was coated with a thin layer of Engineers' marking blue, which visibly indicated the tool-chip contact to have extended well into the textured area.

As compared to responses such as surface roughness and tool life, machining force is a better indicator of lubrication

effectiveness in cutting with respect to repeatability and resolution [11], and hence texture performance was assessed in this work in terms of feed and cutting forces. Fig. 3 indicates the texturing to have brought about a 30% and 13% reduction in the average feed and cutting forces, respectively, which is comparable to that reported in [5] for laser textured tools. The percentage reduction is computed as the difference in force between the non-textured and textured tool relative to the force corresponding to the non-textured tool. Experiments indicated such force reduction to be sustained over extended periods of cutting, with no material build-up on the textured surface.

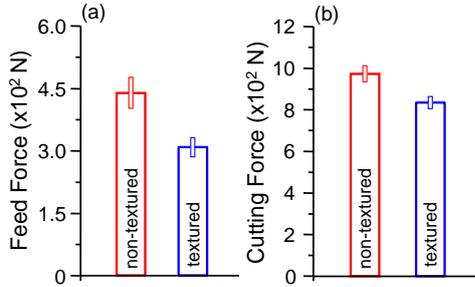


Fig. 3. Effect of texturing on forces in continuous cutting of steel.

As the tool used was of 0° rake angle, the reduction in feed force directly reflects the decrease in the frictional force on the tool rake face. The decrease in cutting force, on the other hand, is a consequence of the coupling between the shear and friction processes in cutting, with the friction reduction increasing the shear plane angle which in turn translates into a thinner chip. In addition to a decrease in the mean forces, texturing also reduces the variability in forces (Fig. 3). Considering that the scatter in machining force is primarily due to variability in the contact zone geometry, this implies that textured tools refer to a more consistent tool-chip contact length. Such features of force reduction were evident also in intermittent cutting (Fig. 4) for conditions identical to that in continuous cutting, with the exception that the feed force reduction was more pronounced. This is interpreted in the following, in the context of the role of cutting parameters.

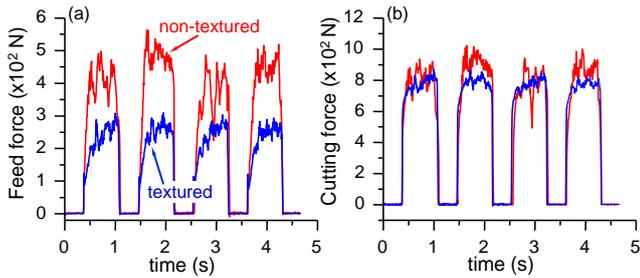


Fig. 4. Effect of texturing on forces in intermittent cutting of steel.

The effectiveness of the texture in reducing the feed force decreases with an increase in cutting speed and feed (Fig. 5a). This is consistent with the insight gained from an analysis in [1] that the distance to which the lubricant penetrates into the contact zone is inversely proportional to both the cutting speed and the feed. In a physical sense, lubrication effectiveness reduces with an increase in cutting speed, as lubricant ingress into the contact zone is retarded, and there is less time available for it to react with the chip. There is also the likelihood of lubricant breakdown at the elevated interface temperatures associated with increased speeds. With an increase in feed, the contact length increases and hence the distance to which the lubricant penetrates relative to the increased contact length is lower, thereby rendering it less

effective. Such aspects are less of an issue in intermittent cutting, as the lubricant is repeatedly replenished directly over the rake face during the non-cutting interval. Accordingly, the reduction in feed force in intermittent cutting is higher than that in continuous cutting at all cutting speeds tested (Fig. 5b). Further tests indicated the efficacy of the texture to diminish with an increase in the ratio of cutting to non-cutting intervals.

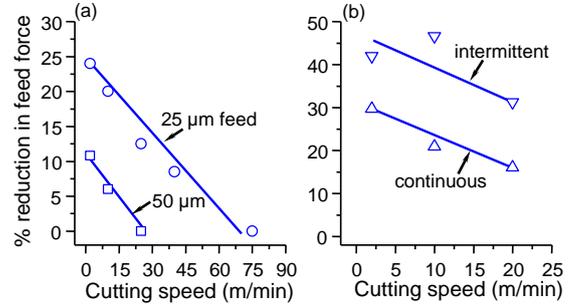


Fig. 5. Effect of cutting speed on force reduction with respect to: (a) feed ($d_e = 0.06$ mm) and (b) process configuration ($h = 0.1$ mm, $d_e = 0.2$ mm).

Force traces from experiments conducted to assess the extent of force reduction when cutting aluminum are shown in Fig. 6. The reduction in the forces as well as the associated variability is quite high, as compared to when cutting steel (Fig. 3). On further investigating this extraordinary force reduction, it was recognized that the lubricant used during the course of experiments was specifically formulated for cutting aluminum.

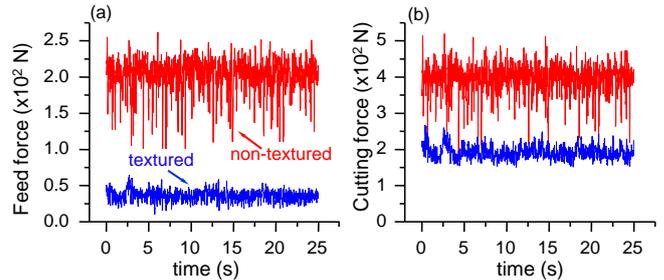


Fig. 6. Effect of texturing on forces in continuous cutting of aluminum.

There are two considerations in designing the position of the texture relative to the cutting edge. Extending the texture right to the cutting edge ($d_e = 0$ in Fig. 1a) was counterproductive as it increased the forces relative to a non-textured tool, due to spark erosion rounding-off the cutting edge, which increased the nominal edge radius from 5 μ m to 25 μ m. The texture stopping short of the edge can further be beneficial in averting possible catastrophic tool failure that could arise from the adverse surface integrity effects of EDM, especially for tools with a low toughness and/or a small wedge angle. In fact, lubricants cannot penetrate the contact zone in the vicinity of the cutting edge even at cutting speeds approaching zero [1], and hence there is little motivation for texturing this region in the first place. Fig. 7

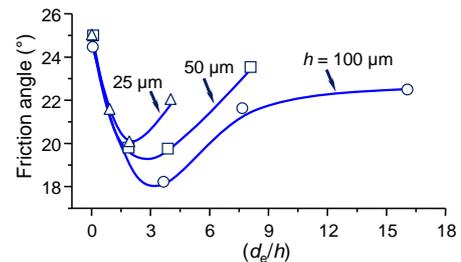


Fig. 7. Effect of texture location on friction angle.

shows the friction angle to be minimum when d_c is roughly 2–3 times the feed h , beyond which the tool tends to be a non-textured one. Considering that the tool-chip contact length is typically about 4–6 times the feed, this implies that it is practical to texture just the sliding region, assuming the sticking and sliding zones to be roughly of equal length.

The force reduction associated with the linear texture (Fig. 1b) increases in proportion to the texture density (Fig. 8), which was altered by varying the pitch between the grooves. The 100% textured area refers to the areal texture (Fig. 1a), which makes it evident that this texture is to be preferred over the linear one. It is indeed conceivable to develop a hybrid texture that integrates areal and linear textures to further facilitate lubricant penetration, with the linear texture oriented obliquely to the chip velocity vector, so as to minimize shear flow-induced lubricant egress.

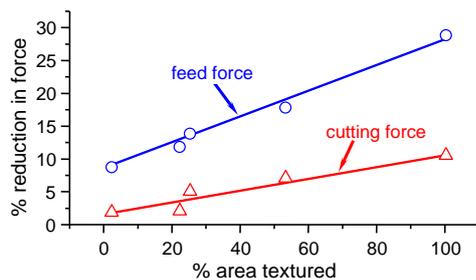


Fig. 8. Influence of textured area on machining force.

Extensive preliminary tests involving EDM spark energy levels over a wide range indicated the force reduction to be maximum at a current i_e of 39 A and an on-time t_i of 42 μ s, which referred to a texturing time of about 10 seconds. The corresponding texture was of a roughness of $\sim 12 \mu$ m R_a , which is fairly coarse compared to most functional surfaces. Despite the pulse parameters being rather aggressive, the process was observed to be benign enough to not induce catastrophic tool failure. Surface traces of the textured area were acquired using a stylus profilometer in an attempt to characterize the texture in terms of indices that correlate with the extent of force reduction. Lubricant infiltration into the contact zone is critically influenced [1] by the nominal height of the micro-channels that relates to the roughness of the texture; however, force reduction examined in terms of the R_a parameter exhibited much scatter to be of use in formulating guidelines for texture design. Likewise, the reduction in forces did not manifest any trends with respect to either i_e or t_i .

In contrast to the above, force reduction revealed defined maxima in terms of the skewness and kurtosis of the texture (Fig. 9), which respectively signify the degree of asymmetry and sharpness of the surface height distribution. The values reported in Figs. 9a and 9b each refer to the average of 20 measurements, and span the envelope typical of surfaces generated in EDM [10]. The maximum force reduction was realized at a skewness of

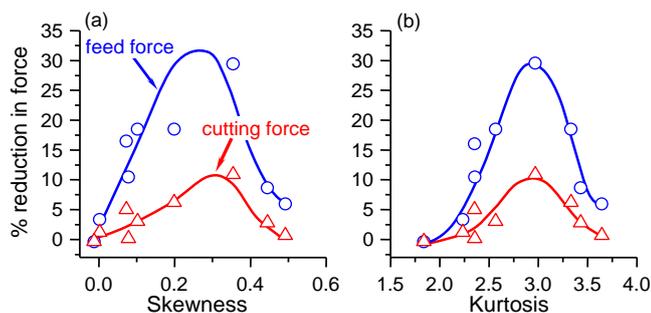


Fig. 9. Role of skewness and kurtosis on force reduction.

approximately 0.3 that relates to a surface wherein the number of valleys exceeds the number of peaks at a certain height, and a kurtosis of about 3 that refers to a surface with no inordinately high peaks or low valleys. In perspective, it is interesting to note that these numbers are in line with a prescription for low-friction surfaces of magnetic recording media [12], despite the orders of magnitude difference in surface roughness and contact forces between these applications.

4. Conclusions

Electrical discharge texturing of cutting tools has been demonstrated to bring about a significant reduction in machining force through enhanced lubrication of the tool-chip interface. A continuous texture with overlapping craters typical of surfaces machined in EDM was found to be more effective than a linear texture comprising a series of grooves. In order to maximize force reduction, it was shown that the texture need be situated away from the cutting edge at a distance that depends on the feed. The skewness and kurtosis of the texture heights have further been found to be good indicators of the extent of force reduction.

As texture performance is maximized in interrupted cutting and at low speeds, the concept is attractive for broaches, taps and gear cutting tools, particularly in the machining of heat resistant alloys that severely limit the cutting speed. The idea may also find application in metal forming tools. For tools that entail the powder metallurgy route, the possibility of imprinting said texture during the compaction process, as opposed to using EDM on the finished insert, may be explored for enhanced throughput and surface quality.

Acknowledgements

This work was funded by the AUTO21 Network Centre of Excellence, and the Natural Sciences and Engineering Research Council of Canada.

References

- [1] Childs THC et al, 2000, *Metal Machining: Theory and Applications*, John Wiley, New York.
- [2] Bruzzone AAG et al, 2008, Advances in engineered surfaces for functional performance, *Annals of the CIRP*, 57/2:750-769.
- [3] Enomoto T, Sugihara T, 2010, Improving anti-adhesive properties of cutting tool surfaces by nano/micro-textures, *Annals of the CIRP*, 59/1:597-600.
- [4] Kawasegi N et al, 2009, Development of cutting tools with microscale and nanoscale textures to improve frictional behavior, *Precision Engineering*, 33:248-254.
- [5] Lei S, Devarajan S, Chang Z, 2009, A study of micropool lubricated cutting tool in machining of mild steel, *Journal of Materials Processing Technology*, 209:1612-1620.
- [6] Jiang W, Malshe AP, Wu JH, 2007, Bio-mimetic surface structuring of coating for tribological applications, *Surface & Coatings Technology*, 201:7889-7895.
- [7] Dumitru G et al, 2005, Femtosecond laser processing of nitride-based thin films to improve their tribological performance, *Applied Physics A*, 80:283-287.
- [8] Zhu D et al, 2009, Electrochemical micromachining of microstructures of micro hole and dimple array, *Annals of the CIRP*, 58/1:177-180.
- [9] Aspinwall DK et al, 1992, Electrical discharge texturing, *International Journal of Machine Tools and Manufacture*, 42:183-193.
- [10] Whitehouse DJ, 1994, *Handbook of Surface Metrology*, Institute of Physics Publishing, Bristol.
- [11] De Chiffre L, Belluco W, 2000, Comparison of methods for cutting fluid performance testing, *Annals of the CIRP*, 49/1:57-60.
- [12] Bhushan B, 1998, Method of texturing a magnetic recording medium for optimum skewness and kurtosis to reduce friction with a magnetic head, United States patent 5,737,229.